

# EFFECTS OF SEAWATER ON AAR EXPANSION OF CONCRETE

A. Shayan<sup>1,\*\*</sup>, A. Xu<sup>1</sup>, G. Chirgwin<sup>2</sup> and H. Morris<sup>2</sup>

<sup>1</sup> ARRB Group Ltd, MELBOURNE, Australia

<sup>2</sup> RTA, NSW, SYDNEY, Australia

## Abstract

Recently, AAR was identified in submerged piles of some RTA bridges in tidal water. Microstructural examination detected chloroaluminate salts in some cracks. To clarify whether seawater had influenced the deterioration an experimental program was planned to examine the effects of sodium chloride on AAR under various curing conditions.

Concrete prisms containing either of reactive, slowly reactive or non-reactive aggregate, and either low or high alkali contents were stored in salt solution or at 100% RH, at temperatures of 38, 60 and 80 °C, for expansion measurement for one year, after which the temperature was lowered to 23°C to check its effect on further expansion, which could be attributed to precipitation of ettringite and/or chloroaluminate

The results indicate the type of aggregate and concrete alkali content had the greatest effect on AAR expansion. Exposure to salt solution (seawater) did not have any significant effect on the AAR expansion.

**Keywords:** AAR; Expansion; Curing-temperature; Alkali-content; Salt-solution

## 1 INTRODUCTION

It is known that alkali-aggregate reaction (AAR) can cause serious cracking and deterioration of concrete structures, particularly those in moist environments. The requirements for AAR to occur in the concrete are the presence of sufficient amounts of reactive components, alkali and moisture, and the mechanisms of the reaction are well established. AAR has been identified in many locations worldwide to have caused damage to structures exposed to a variety of environmental conditions, including de-icing salts and marine conditions. The latter are more aggressive than normal exposure conditions as the concrete is subjected to the effects of a number of salts present in the seawater. The salt content of seawater is broadly about 3.5%, and its composition includes about 19400 ppm Cl, 10800 ppm Na, 1290 ppm Mg, 900 ppm S, 410 ppm Ca, and 390 ppm K, among numerous other elements of far less abundances.

Extensive research in the past few decades has established the mechanisms of seawater attack on cement paste and concrete, and shown that seawater certainly causes deterioration of cement paste as a result of reaction with susceptible components of the paste, and formation of new reaction products such as gypsum, ettringite, brucite, calcium-chloroaluminate phases (Friedel's salt) and magnesium silicate hydrate (e.g. Kalousek and Benton, 1970 [1]; Regourd, 1980, 1982 [2, 3]; Sayward, 1984 [4]).

The seawater can probably adversely affect the behaviour of concrete containing reactive aggregates and enhance the deterioration. It has, in fact, been implicated in the mechanisms of AAR. For instance, the Danish accelerated AAR test, as used by Chatterji, et al. (1987) [5] for testing a flint aggregate, involves storage of concrete or mortar specimens in saturated NaCl solution at 50 °C. Swamy and Al-Asali (1987) [6] showed that storage of concrete prisms (cement content of 520 kg/m<sup>3</sup>), containing fused silica or opal as aggregate, in a 4% NaCl solution resulted in a higher expansion compared to storage in water. The latter authors [5, 6] did not report the composition of the cements used. It should be noted that storage in water [6] leads to leaching of alkali and reduced expansion compared to storage at 100% RH.

Addition of NaCl to mortar or concrete mixes, at the time of casting, Nixon, et al. (1987) [7], had the same effect as using Portland cements with higher native alkali contents. This effect was stated to arise from the reaction of the added NaCl and the C3A component of cement, which released OH ions into the pore solution of concrete, thereby exacerbating AAR expansion of their flint-bearing specimens. The cement used had 11.7% C3A, which is far greater than that in modern cements (~5%), and would generate correspondingly more OH in the concrete as a result of this reaction.

Storage of specimens in seawater or NaCl solutions has been shown [8-11] to enhance AAR expansion, partly due to increased alkalinity arising from reaction with the aluminates, but the authors concerned did not fully explain why extra expansion took place. Kawamura, et al (2000) [12], also observed that mortar specimens expanded more in NaCl than NaOH solution, and attributed this to the formation of AAR gel with low alkali content. They found ettringite in AAR-induced microcracks, but could not state whether the presence of ettringite contributed to the expansion. However, work by the present author showed that unless elevated alkali levels were present, the

---

\* Correspondence to: [ahmad.shayan@arrb.com.au](mailto:ahmad.shayan@arrb.com.au)

presence of the saturated NaCl solution per se did not induce AAR expansion in concrete prisms [13]. Duchesne and Berube (1996) [14] also arrived at the same conclusion. This may have been a result of the Australian aggregates used being slowly reactive compared to the Danish aggregates. The interaction of NaCl with the C3A (calcium aluminate) phase of cement generates Friedel's salt, and results in the dissolution of portlandite and formation of extra alkali hydroxide in the concrete pore solution, which is the reason for the enhanced expansion.

Based on mineralogical investigation of the cementitious systems under the accelerated testing conditions, Shayan (1998) [15] suggested that there may be a different reason for the extra expansion, which would be analogous to the mechanism of expansion caused by delayed ettringite formation. The process was suggested to concern formation of Friedel's salt and to involve paste expansion and filling of microcracks, similar to the case of DEF. Inspection and scrutiny of some published AAR expansion results for a reactive aggregate, presented in [11], strengthened the belief that such a mechanism may be operative. It was suggested that the formation of calcium chloroaluminate phases in AAR-induced microcracks in their concrete prisms could have exacerbated the expansion. Shayan and Morris (2006) [16] found field evidence for this mechanism in the examination of deteriorated concrete bridge piles, in which compact layers of chloroaluminate were found in AAR-induced microcracks, in the same morphological form as that of expansive ettringite in heat-cured concrete. However, there is no proof that this caused deleterious expansion.

If Friedel's salt formation in the paste, or its precipitation into AAR-induced microcracks, can cause additional concrete expansion, then the type of aggregate, the alkali and aluminate contents, precasting temperature and exposure to salt water would all contribute to the expansion and deterioration of elements subjected to salt water. Consequently, precautions, in addition to the usual steps taken to avoid AAR damage, may be necessary for elements immersed in salt water. This could also have implications for the testing environment of mortar bars or concrete prisms, and the prediction of performance of concrete elements submerged in salt water.

Recent observation of significant deterioration of some precast, prestressed, AAR-affected bridge piles in marine conditions [16] has highlighted the need to investigate the possible influence of seawater on AAR expansion and cracking. This paper presents the results of testing aggregates of varying reactivity under standard AAR test conditions, in comparison to those obtained at different alkali levels, varying temperatures, and under salt water exposure, and discusses the influence of salt water on the expansion of AAR-susceptible elements in tidal waters.

## 2 EXPERIMENTAL WORK

### 2.1 Materials and procedures

Details of aggregates used are given in Table 1 together with their expansion results when tested by the RTA T363 method. Other ingredients of the concrete mixes are given below.

*Sand:* Non-reactive concrete sand from Excel quarry.

*Cement:* Blue Circle GP cement with Na<sub>2</sub>O equivalent of 0.5%.

*Cement alkali level:* Original alkali content (0.5%) and elevated alkali (1.4 %) as Na<sub>2</sub>O equiv. The additional alkali was added in the mixing water at the time of casting the specimens.

*Cement content of concrete:* 420 kg /m<sup>3</sup>, W/C ratio of 0.45, ( RTA T364 Concrete Prism Test (CPT)

*Curing and storage temperature:* 38°C (RTA T364 and ASTM C 1293 condition) , 60 °C (Rilem Concrete Prism Test condition) and 80 °C (Steam curing condition, also RTA T363 storage temperature). The expansion criteria for these tests are, respectively, 0.03% at one year (note: ASTM C1293 limit is 0.04%); 0.03% at 3-4 months; and no agreed limit for concrete prisms tested at 80°C in 1M NaOH.

*Calcium aluminate content of cement:* 5.5 % C<sub>3</sub>A and 10.2 % C<sub>4</sub>AF

*Exposure:* 100% RH and a salt solution comprising 5% NaCl + 0.72% Mg SO<sub>4</sub>. The 5% salt solution was slightly more concentrated than seawater (3.5% salt) to ensure adequate supply of the salt to the specimens. The MgSO<sub>4</sub> content was the same as 0.06M, the average Mg concentration in seawater.

### 2.2 Concrete mix combinations

Table 2 shows Details of the aggregate types used, the alkali content, curing temperature and exposure conditions of the various specimens. The total number of concrete mixes was 6. Each mix comprised 12 concrete prisms, four at each temperature. For the normal concrete prism test (CPT) a set of two prisms were stored under 100% RH at 38 °C, and two in the salt solution at 38 °C.

For the CPT at 60 °C, the specimens were stored in sealable boxes either at 100% RH (i.e. the Rilem CPT) or containing the salt solution. The boxes were then placed in a sealed constant temperature bath kept at 60 °C. The specimens for the 80 °C test were treated similarly to those at 60 °C, but the sealed boxes were placed in an oven kept at 80 °C rather than in a bath. Each expansion measurement was the average of the expansion values for two prisms.

Examination of results at about 290 days showed that the expansion values had dropped after 200 days for a number of specimens especially those held in hot (80°C) storage conditions, which appeared to be a systematic trend. It was thought either the poor sealing of the relevant containers and loss of moisture, or some chemical changes occurring at high temperature could have caused this drop. Consequently, containers with salt solution were

moved, into the 23°C constant temperature room at exposure age of 293 days. These specimens remained in this condition since then to the end of measurement period.

Specimens that were subjected to humid air exposure remained in their conditions. The containers with specimens at 80°C air exposure were moved into the water tank with the lid sealed at 290 days. This tank has ensured a more humid condition than that when the oven was used. Expansion was measured after some 100 days to check whether the drop in expansion has recovered.

In addition, at the end of one year the other specimens which had been stored in seawater at 38°C and 60°C were transferred to a constant temperature room at 23°C, and measurements continued under this condition for a long period. This was to check whether a drop in temperature would lead to additional expansion which could be attributed to precipitation of ettringite and/or chloroaluminate in the microcracks. Note that all the specimens, regardless of storage temperature, were equilibrated at 23°C for 24 hours prior to expansion measurement.

### 3 RESULTS AND DISCUSSION

The compressive strength results for the six concrete mixes were presented in Table 3. The strength of mixes containing the additional alkali is lower than the corresponding mixes without the added alkali, which is expected.

The expansion of concrete specimens up to around 600 days are summarised in Figures 1-3 for the non-reactive, slowly-reactive and reactive aggregate types, respectively. Figure 1 shows that the concrete prisms containing the non-reactive aggregate did not expand deleteriously under any condition. Therefore, storage conditions and alkali levels per se would not cause any AAR-related deterioration, in the absence of a reactive aggregate. However, it appears that storage in seawater at both 60°C and 80°C may have a minor effect on the cement paste, as the recorded expansion values were slightly higher under these conditions.

Figure 2 shows that, as expected, the concrete prisms containing the slowly-reactive aggregate did not expand deleteriously at low alkali content, under any storage condition. However, as stated for the data in Figure 1, it seems that, storage at high temperature in seawater may lead to minor expansion of the paste. This implies that seawater would not cause AAR expansion, if the original amount of alkali in the concrete is inadequate.

The results for specimens containing low alkali appear to show a systematic error as all the expansion values show a drop after 190 days of exposure. This was thought to have arisen from loss of moisture, but it also happened for specimens stored in solution. In fact, moving the container which originally had the specimens at 80°C in salt solution to the 23°C condition room only partially recovered the drop in expansion. It appeared that a faulty thread in the specimen holder anvil in the comparator had caused this problem, which has been fixed. Nevertheless, the conclusion highlighted above remains valid.

Specimens containing the slowly reactive aggregate showed significant expansion at high alkali content and high temperature. Despite the high alkali content, expansion at 38°C was low in both 100% RH and in salt solution, due to the nature of the aggregate. This type of aggregate may need to be monitored for expansion for two years before CPT can become conclusive. This is an example of the type of aggregate for which the CPT test at 38°C is not conclusive, and the Rilem CPT at 60°C is a better option. Experience at ARRB shows that the Rilem CPT (100% RH, 60°C) is most suitable for slowly reactive aggregates containing microcrystalline/strained quartz, for which neither the Australian CPT (RTA T364), nor the ASTM C-1293 CPT give satisfactory results in one year, whereas the Rilem test produces conclusive results in 3-4 months.

The 60°C, 100% RH storage condition gave the highest expansion, followed by 80°C at 100% RH. It must be pointed out that the 60°C 100% RH test was carried out in a reasonably sealed box, stored in a large sealed water bath (where no moisture loss was possible), whereas the 80°C, 100% RH test was in a similar box stored in an oven where, it appears, moisture loss could not be prevented. The latter condition resulted in considerable moisture loss from the box, which must have had an adverse effect on the expansion (also indicated by checking the mass change of specimens).

The steel container for specimens at 80°C, 100% RH was moved from the 80°C oven to a water tank kept at 80°C (which stopped any moisture loss), at the age of 290 days and left undisturbed for three months, after which the mass was checked and expansion measured. The mass had almost recovered to that of the early age before drying occurred, and the expansion also recovered, as shown for the measurement at 390 days. Nevertheless the 80°C expansion was lower than the 60°C, which may be related to chemical destabilisation of some hydration products such as ettringite at 80°C. There was little difference in the expansion in seawater between the 60°C and 80°C temperatures, as it appears that in both cases, the leaching of alkali was probably the main factor in not achieving the full expansion potential compared to 60°C at 100% RH.

Ehtesham Hussein and Rasheeduzzfar (1993) [17] reported that the concentration of hydroxyl ions in the pore solution of their specimens was significantly reduced at 70°C compared to 20°C, and that in the presence of chloride the concentration of Cl in the pore solution increased correspondingly. In the context of the present experiments this would lead to leaching of hydroxyl ions and reduction in alkalinity.

Storage in seawater at 60°C and 80°C resulted in lower expansion at both temperatures than the corresponding expansion at 100% RH and the same temperatures, which indicates that seawater did not promote AAR. On the contrary, the salt solution storage condition most likely resulted in the leaching of alkali hydroxide from the high-alkali specimens, and consequently reduced the AAR expansion. These results agree with previous

results [13] obtained on some Australian aggregates subjected to the Danish test (Saturated NaCl solution at 50 °C). It is important to note that the 60 °C, 100% RH was the best condition for revealing the expansion potential of this aggregate. This is, in fact the conditions used for the Rilem Concrete Prism Test (CPT60). A separate paper is presented at this conference by Shayan and Xu (2008) [18] on testing 50 aggregates by the Rilem CPT method.

Figure 3 shows the results for the reactive aggregate which, for the low alkali content parallel those for the slowly-reactive aggregate. Note that at 300 days, specimens in 100% RH environment were not measured so as not to disturb them and keep the humidity continuously until one year of age. For the high alkali content, the concrete specimens in 100% RH, 38 °C and 100% RH, 60 °C reached the same final expansion of about 0.10%, which indicated high reactivity. However, deleterious expansion was reached in a much shorter time at 60 °C than at 38 °C.

The specimens at 80 °C, 100% RH, expanded only half the amount reached at 38 °C or 60 °C, which could be due to the destabilisation of ettringite at 80 °C and probably other chemical changes. Results of Shayan (1998) [15] clearly showed this effect for both ettringite and chloroaluminate salts. It has also been shown by Ogawa and Roy (1982) [19] that the presence of chloride reduced the expansive effect of ettringite formation due to substitution of Cl in the ettringite structure, and formation of less expansive minerals.

The results obtained here contradict those of Kawamura et al (1996) [20] who reported that expansion of mortar bars made with calcined flint aggregate increased after storage in IM NaCl solution at 38°C when the alkali content of the mortar was high. They attributed the additional expansion partly to the increase in hydroxyl ion concentration and partly to enhanced ettringite formation in the presence of NaCl solution. The present results also contradict those of Swamy and Al-Asali [6] who used opal and fused silica as aggregate and storage conditions of 4% NaCl solution at 40°C. The difference in the behaviour of specimens used in these studies and those used in the present study may be related to the very different natures of the aggregates used in the two studies. It is also possible that the cements used by the latter authors ([20], [6]) were very high in C3A, similar to that used by Nixon, et al. [7], and its reaction with salt water generated sufficient OH ions to promote AAR in their specimens. Therefore, the nature of the aggregate and the cement type in the concrete could have a significant effect on its interaction with salt water.

In another study Kawamura and Takeucki (1996) [21] found that only when hydroxyl concentration in the pore solution was high, NaCl or seawater could accelerate alkali silica reaction at 20°C. They stated that the reaction proceeded differently at 38°C in IM NaCl solution, by an increase in the hydroxyl concentration in the presence of chloride ions. The present work shows that the level of alkali hydroxyl in the specimen was the determining factor with respect to AAR expansion, and that the presence of salt solution did not play a role because in our low alkali specimens additional hydroxyl ions were not produced, at least to the extent that could cause deleterious expansion.

All the specimens kept in seawater expanded much less than their counterparts at 100% RH, which is attributed to the leaching of alkali from the specimens. Therefore, storage in seawater did not contribute to the expansion of the concrete prisms made with reactive aggregate. It should be noted that the leaching of alkali from the relatively small concrete prisms, may be translatable to large elements such as piles submerged in seawater.

Although the RTA T363 accelerated mortar bar test results, obtained previously for the coarse aggregates, were much higher for the reactive aggregate (0.45%) compared to the slowly-reactive aggregate (0.118%), the results of CPT at 60 °C, 100% RH were similar (~0.10%) for both aggregates, indicating that the 60 °C, 100% RH test is most suitable for the detecting the slowly reactive aggregates.

Overall, it appears that exposure of concrete to the salt solution at elevated temperature, even though it may contain aggregates susceptible to AAR, does not exacerbate the AAR problem. On the contrary, it may cause leaching of alkali from the specimens and reduction in expansion.

For all the specimens stored in salt solution, which were transferred to 23°C in their containers at the age of about 300 days, no further expansion was subsequently noted, as seen in Figure1-Figure3, during the storage period up to the age of about 450 days. Therefore, the effects of lowering the storage temperature to 23°C on further expansion, which could be attributed to precipitation of ettringite and/or chloroaluminate was found to be negligible.

#### 4 CONCLUSIONS

The results obtained so far indicate that the type of aggregate and alkali content of concrete have the greatest effect on AAR expansion. Unlike some results in the published literature, the exposure to salt solution (seawater) at elevated temperature did not have a significant effect on the AAR expansion. The difference may be attributed to the differences in the nature of aggregates as well as the C3A contents of cements used by those authors. It is recommended that these factors be investigated in future studies.

The possible effects of lowering the storage temperature, from 60°C and 80°C to 23°C, on further expansion, which could be attributed to precipitation of ettringite and/or chloroaluminate, was measured during a prolonged storage period of 300 days at 23°C, and was found to be negligible. It appears that the deterioration of the prestressed piles reported by Shayan and Morris (2006) [16] was mainly due to AAR and DEF, and that the exposure to seawater did not have a primary role in the deterioration of the affected piles.

## 5 DISCLAIMER

The opinions expressed in this paper are those of the authors, and do not necessarily reflect the policies or practices of their supporting organisations

## 6 REFERENCES

- [1] Kalousek, G.L. and Benton, E.J (1970): Mechanism of seawater attack on cement pastes, *ACI Journal*, February issue, pp. 187-192.
- [2] Regourd, M. (1980): Physico-chemical studies of cement pastes, mortars and concretes exposed to seawater. In: *Performance of concrete in marine environment*, ACI publication SP-65, pp. 63-82.
- [3] Regourd, M. (1982): Chemical durability of concrete, In: *Contemporary European Concrete Research*, Swedish Cement and Concrete Research Institute, pp. 121-14.
- [4] Sayward, J.M. (1984): Salt action on concrete, Special Report 84-25, US Army Corps of Engineers, Cold regions Research & Engineering Laboratory, Hanover, New Hampshire, 76 pp.
- [5] Chatterji, S., Thaulow, N., Jensen, A.D. and Christensen, P. (1987): Mechanism of accelerating effects of NaCl and Ca(OH)<sub>2</sub> on alkali-silica reaction. *Proc. 7<sup>th</sup> IAARC*, Ottawa, Canada, pp. 115-119.
- [6] Swamy, R.N. and Al-Asali, M.M. (1986): New test methods for alkali-silica reaction, In: *Concrete alkali-aggregate reaction*, *Proc. 7<sup>th</sup> Int. AAR Conf.* Ottawa, Canada, P.E. Grattan-Bellew (editor), pp. 324-329.
- [7] Nixon, P.J., Canham, I., Page, C.L. and Bollinghaus, R. (1987): Sodium Chloride and alkali-aggregate reaction. *Proc. 7<sup>th</sup> IAARC*, Ottawa, Canada, pp. 110-114.
- [8] Sibbick, R.G., and Page, C.L. (1996): Effects of sodium chloride on the alkali-silica reaction in hardened concrete, *Proc. 10<sup>th</sup> Int. AAR Conf.*, Melbourne, Australia A. Shayan (editor), pp. 822-829.
- [9] Yonezawa, T., Ashworth, V. and Procter, R.P.M. (1989): The mechanism of fixing Cl by cement hydrates resulting in the transformation of NaCl to NaOH, *Proc. 8<sup>th</sup> Int. AAR Conf.*, Kyoto, Japan, Okada, Nishibayashi, and Kawamura (editors), pp. 153-160.
- [10] Kawamura, M., Takeuchi, K. and Sugiyama, A. (1996): Mechanism of the influence of externally supplied NaCl on the expansion of mortars containing reactive aggregate. *Magazine of Concrete Research*, 48, No. 176, pp. 237-248.
- [11] Berube, M.A. and Frenette, J. (1994): Testing concrete for AAR in NaOH and NaCl solutions at 38°C and 80°C, *Cement and Concrete Composites*, 16 (3), pp. 189-198.
- [12] Kawamura, M., Arano, N. and Katafuta, K. (2000): ASR gel composition secondary ettringite formation, and expansion of mortars immersed in NaCl solution, Translation from *Proc. JSCE*, No641/V-46, February 2000, pp. 155-162.
- [13] Shayan, A. (1988): Developments in accelerated testing of aggregates for alkali-aggregate reaction, *Proc. 2nd Australia/Japan Workshop on durability of reinforced concrete structures*, November 1988, CSIRO, DBCE, Highett, Victoria, Australia, pp. 2.47-2.56.
- [14] Duchesne, J. and Berube, M.A. (1996): Effect of de-icing salt and seawater on ASR: New considerations based on experimental data, *Proc. 10<sup>th</sup> Int AAR Conf.*, Melbourne, Australia, A. Shayan (editor), pp. 830-837.
- [15] Shayan, A. (1998): Effects of NaOH and NaCl solutions and temperature on the behaviour of specimens subjected to accelerated AAR tests, *Cement & Concrete Research*, Vol. 28, No. 1, pp. 25-31.
- [16] Shayan, A. and Morris, H. (2006): A case study: Deterioration of precast, prestressed concrete piles in marine environment. *Concrete Plant & precast Technology*, BFT (Germany), Vol. 72, No. 1, pp 38-47.
- [17] Ehtesham Hussein, S. and Rasheeduzzfar (1993): Effect of temperature on pore solution composition in plain cements. *Cement and Concrete Research* Vol. 23, pp 1357-1368.
- [18] Shayan, A. and Xu, A. (2008): Comparative study of the concrete prism test (CPT 60°C, 100% RH) and other accelerated tests. *Proc. 13th IAARC*, Trondheim, Norway, June 2008.
- [19] Ogawa, K. and Roy, D.M (1982): C<sub>4</sub>A<sub>3</sub>S hydration, ettringite formation, and its expansion mechanism: II - Effect of CaO, NaOH and NaCl; Conclusions. *Cement & Concrete Research*, Vol. 12, pp 247-256.
- [20] Kawamura, M., Takeda, T., and Takeuchi, K. (1996): Role of gypsum in expansion of mortars containing reactive aggregate in NaCl solution, *Proc. 10<sup>th</sup> Int AARC*, Melbourne, Australia, pp. 838-845.
- [21] Kawamura, M. and Takeuchi, K. (1996): Alkali-silica reaction and pore solution composition in mortars in sea water. *Cement and Concrete Research*, Vol. 26, pp. 1809-1819.

TABLE 1: List of aggregates used & their AMBT expansion values.

Aggregate reactivity	Rock Type	RTA T363 AMBT* expansion (%)
Non-reactive	Basalt	0.01
Slowly-reactive	Gneissic	0.118
Reactive	Rhyodacite	0.45
Non-reactive	EXL sand	0.120

\* Accelerated mortar bar test: expansion limit for coarse aggregate is 0.10% and for sand 0.15%

TABLE 2: Experimental parameters used in the test program.

Exposure condition	Aggregate Type	Cement alkali (%)	Storage temperature (°C)	No. of combinations
100% RH	Non-Reactive	0.50, 1.40	38, 60, 80	6
	Slowly Reactive	0.50, 1.40	38, 60, 80	6
	Highly Reactive	0.50, 1.40	38, 60, 80	6
Salt Solution (5% NaCl + 0.72% MgSO <sub>4</sub> )	Non-Reactive	0.50, 1.40	38, 60, 80	6
	Slowly Reactive	0.50, 1.40	38, 60, 80	6
	Highly Reactive	0.50, 1.40	38, 60, 80	6

TABLE 3: Concrete strength results.

Mix No.	Aggregate & Alkali	ID	Casting date	28 day compressive strength (MPa)
1	Nr-0.5% alkali	C06/1320	14/02/2006	48.2
2	Nr-1.4% alkali	C06/1321	14/02/2006	38.8
3	Lr-0.5% alkali	C06/1322	16/02/2006	55.1
4	Lr-1.4% alkali	C06/1323	16/02/2006	32.3
5	Hr-0.5% alkali	C06/1324	22/02/2006	51.6
6	Hr-1.4% alkali	C06/1325	22/02/2006	37.0

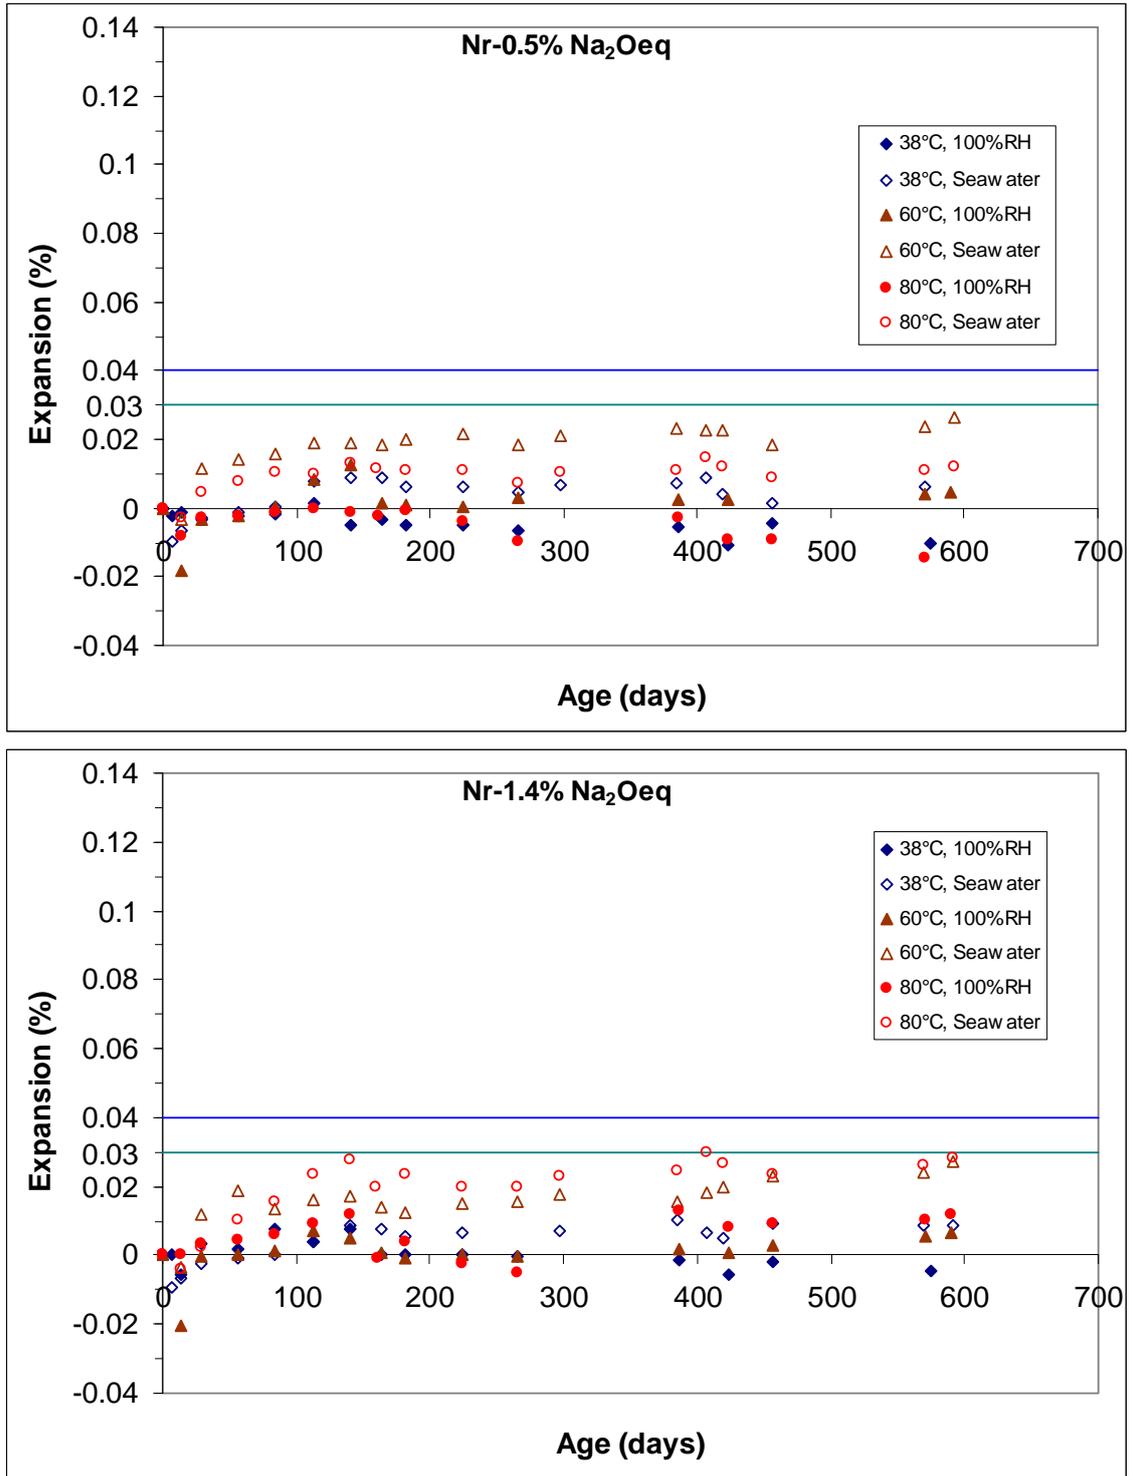


Figure 1: Expansion of concrete prisms made with the non-reactive aggregate, at different alkali contents and under different conditions. Note expansion limits of 0.03% and 0.04% at 1 year for 38°C CPT, and 0.03% at 3-4 months for 60°C CPT.

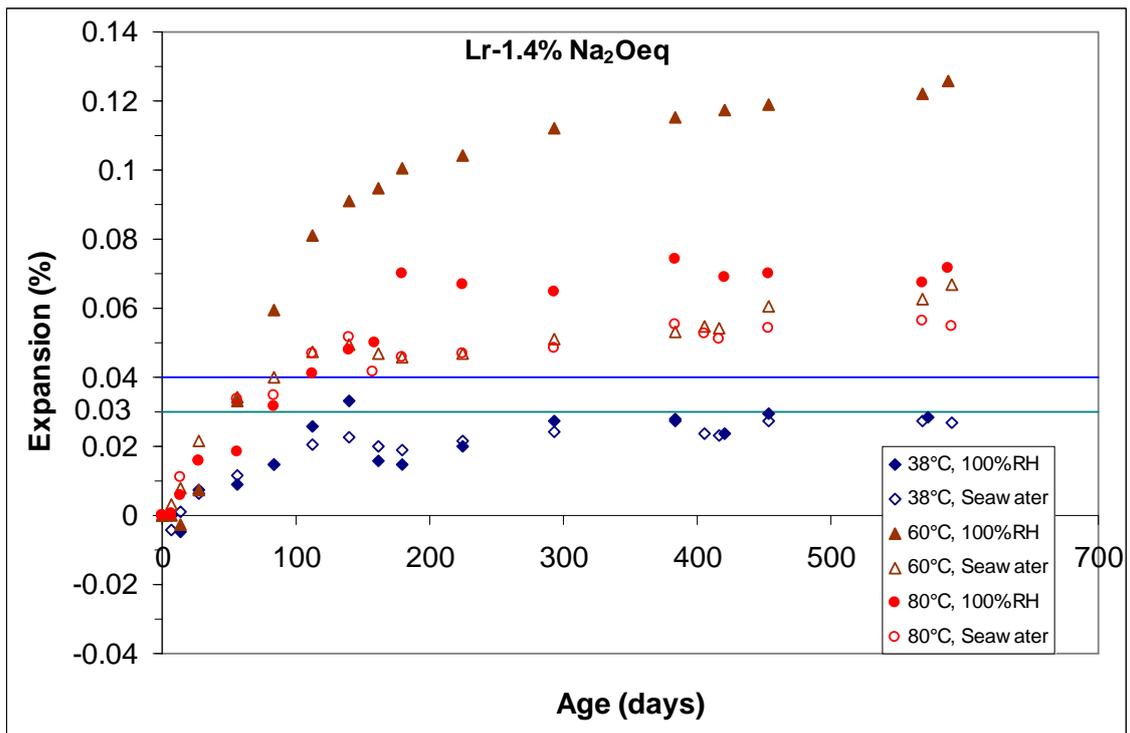
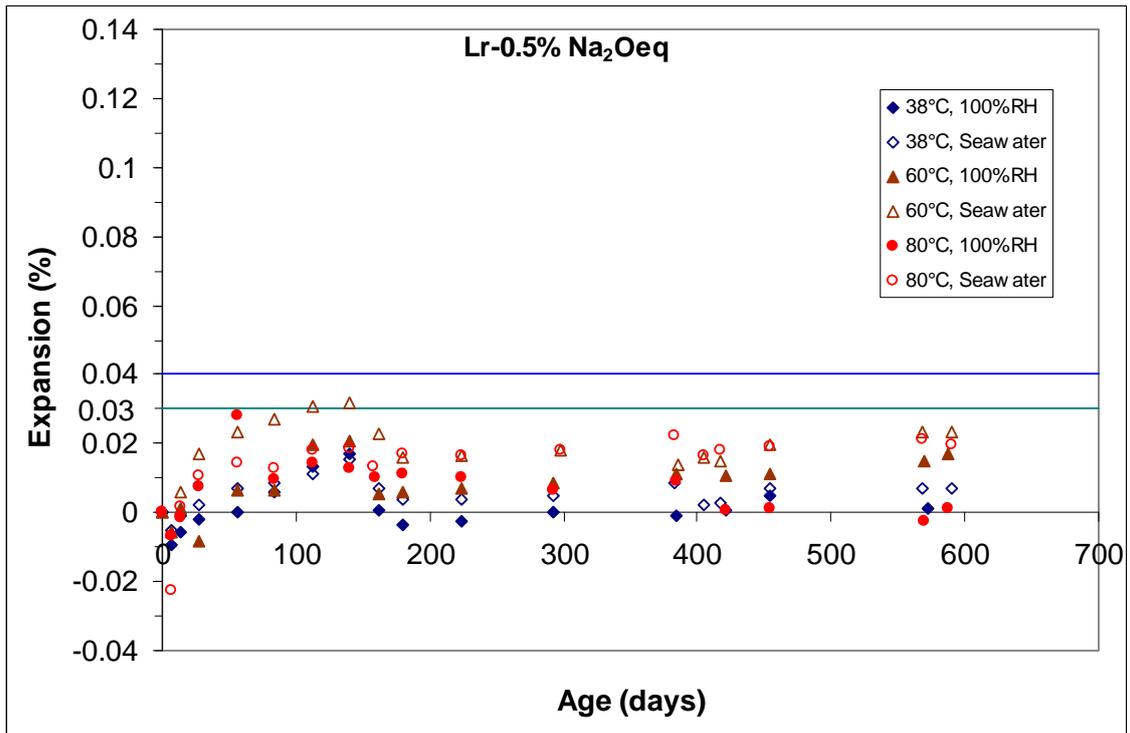


Figure 2: Expansion of concrete prisms made with the slowly-reactive aggregate, at different alkali contents and under different conditions. Note expansion limits of 0.03% and 0.04% at 1 year for 38°C CPT, and 0.03% at 3-4 months for 60°C CPT.

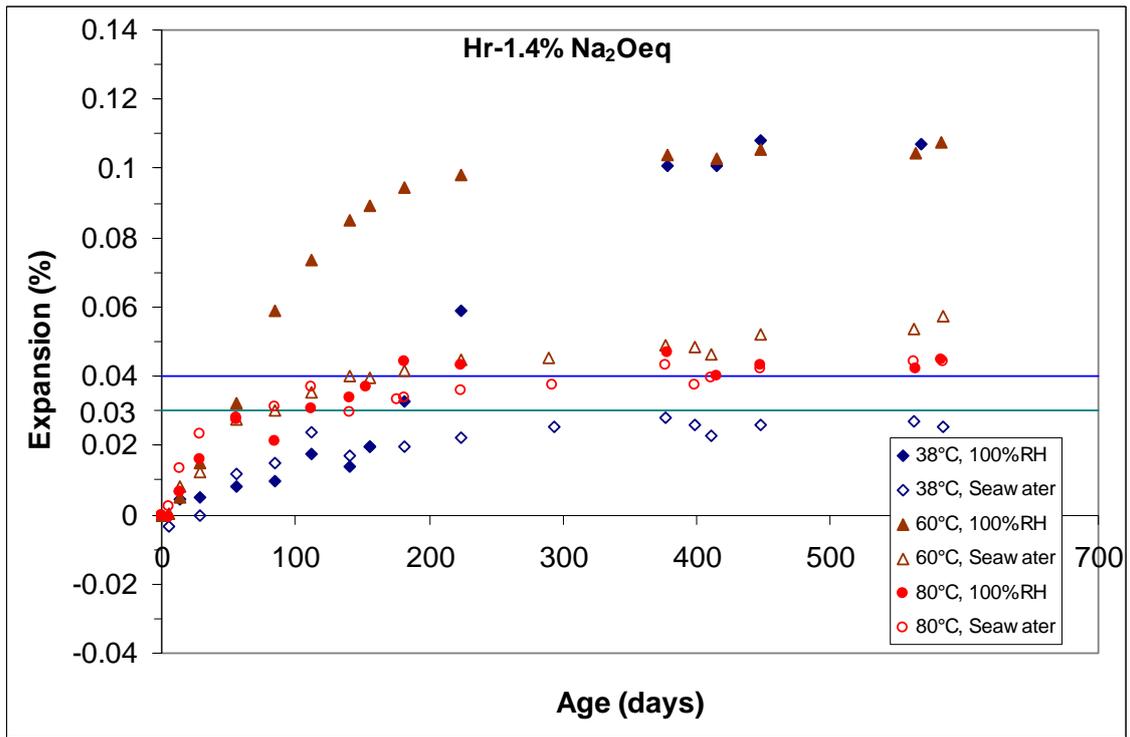
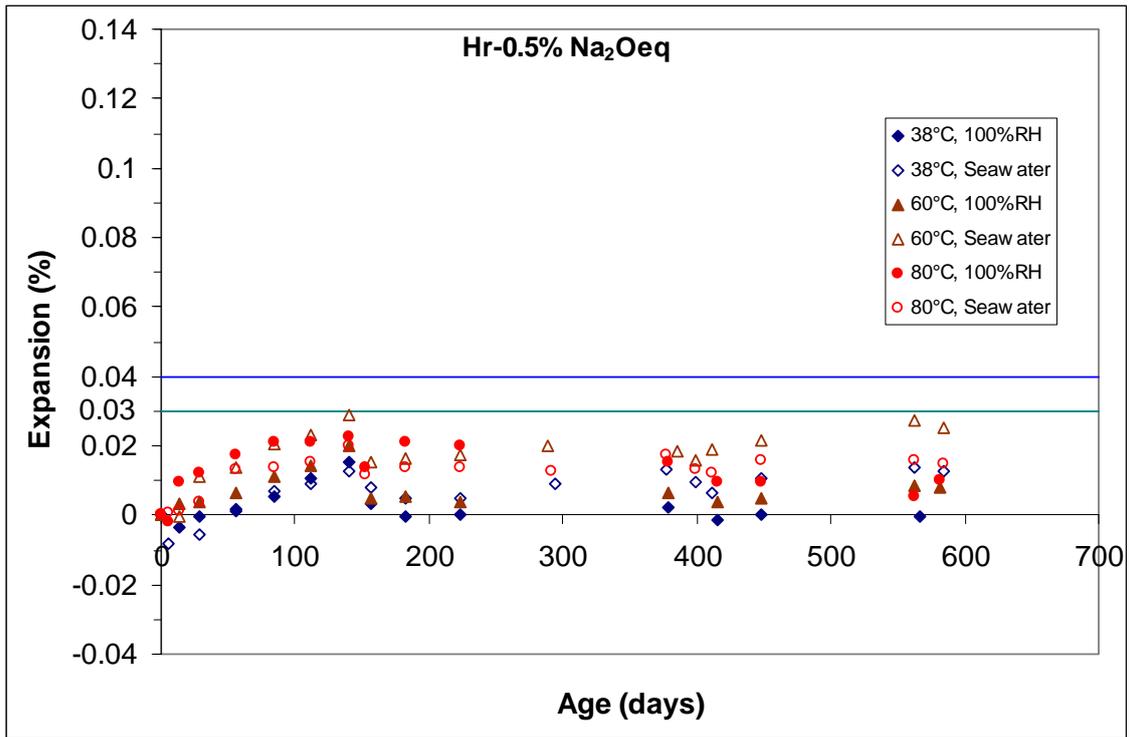


Figure 3: Expansion of concrete prisms made with the reactive aggregate, at different alkali contents and under different conditions. Note expansion limits of 0.03% and 0.04% at 1 year for 38°C CPT, and 0.03% at 3-4 months for 60°C CPT.